

## reFILL

**Cost-effective coarse ground epoxy-glass powder filler that can be used as a circular-economy originated filler for various thermoplastic polymers.**

### PROPERTIES

✓ **Average particle size**


1035 µm

✓ **Particles size range**

~250-3000 µm

✓ **Material composition**

epoxy resin, glass (may contain traces of metals)

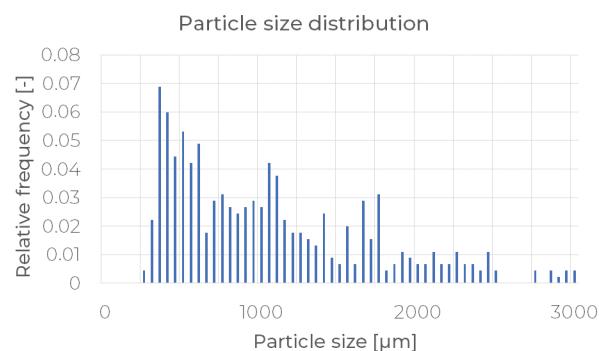

### EFFECT OF 20 WT% ON DIFFERENT TYPES OF POLYPROPYLENE\*

✓ **Polypropylene types**

hPP45 homopolymer, MFR value of 45 g/10 min (230 °C/2.16 kg)

hPP8.2 homopolymer, MFR value of 8.2 g/10 min (230 °C/2.16 kg)

rPP12 random copolymer, MFR value of 12 g/10 min (230 °C/2.16 kg)

bPP13 block copolymer, MFR value of 13 g/10 min (230 °C/2.16 kg)

✓ **Change in properties**

	MFR [g/10 min] 230 °C/2.16 kg	Tensile strength [MPa]	Strain at break [%]	Tensile modulus [MPa]	Charpy impact strength [kJ/m <sup>2</sup> ]
	ISO 1133	ISO 527	ISO 527	ISO 527	ISO 179
hPP45	45	37.2	14	1743	1.4
<b>hPP45+20reFILL</b>	<b>34.3</b>	<b>32.1</b>	<b>5</b>	<b>2087</b>	<b>1.4</b>
hPP8.2	8.2	32.6	22	558	1.9
<b>hPP8.2+20reFILL</b>	<b>6.9</b>	<b>30.1</b>	<b>11</b>	<b>611</b>	<b>1.7</b>
rPP12	12	21.3	145	439	3.2
<b>rPP12+20reFILL</b>	<b>9.3</b>	<b>19.4</b>	<b>100</b>	<b>417</b>	<b>2.2</b>
bPP13	13	23.7	22	511	7.0
<b>bPP13+20reFILL</b>	<b>12.5</b>	<b>21.4</b>	<b>19</b>	<b>534</b>	<b>4.4</b>

\*compounding was made on a Labtech Engineering LTE 26-44 twin screw extruder at 190 °C and 150 rpm. Specimens were injection molded on an Arburg Allrounder 320C 400-170 injection molding machine with the following parameters: melt temperature: 200 °C, mold temperature 30 °C, injection speed 50 cm<sup>3</sup>/s, holding pressure 400 bar.